

AD-A190 523

A NEW APPROACH TO HIGHLY FLUORINATED LUBRICANTS(U)

1/1

DURHAM UNIV (ENGLAND) DEPT OF CHEMISTRY


R D CHAMBERS ET AL. 30 OCT 87 AFOSR-TR-87-1762


UNCLASSIFIED

AFOSR-82-0004

F/G 11/8

NL

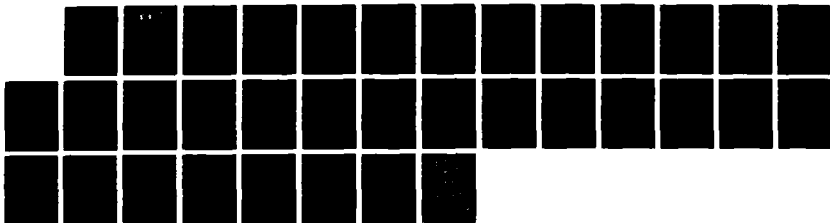

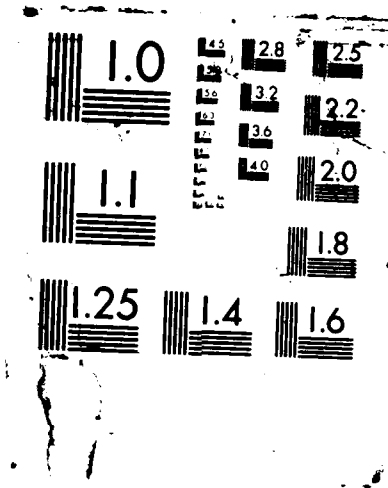

AD-A190 523

## REPORT DOCUMENTATION PAGE

DTIC FILE COPY

(1)

②

Unclassified		1b. RESTRICTIVE MARKINGS	
2a. SECURITY CLASSIFICATION AUTHORITY		3. DISTRIBUTION/AVAILABILITY OF REPORT	
2b. DECLASSIFICATION/DOWNGRADING SCHEDULE		Approved for public release; distribution unlimited.	
4. PERFORMING ORGANIZATION REPORT NUMBER(S)		5. MONITORING ORGANIZATION REPORT NUMBER(S)	
6a. NAME OF PERFORMING ORGANIZATION		7a. NAME OF MONITORING ORGANIZATION	
University of Durham		AFOSR/NC	
6b. OFFICE SYMBOL (If applicable) Department of Chemistry		7b. ADDRESS (City, State, and ZIP Code)	
6c. ADDRESS (City, State, and ZIP Code) Department of Chemistry, University of Durham, Science Laboratories, South Road, Durham, DH1 3LE, U.K.		Bldg 410 Bolling AFB, DC 20332-6448	
8a. NAME OF FUNDING/SPONSORING ORGANIZATION		9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER	
AFOSR		AF OSR 82-0084	
8b. OFFICE SYMBOL (If applicable) NC		10. SOURCE OF FUNDING NUMBERS	
8c. ADDRESS (City, State, and ZIP Code) Bldg 410 Bolling AFB, DC 20332-6448		PROGRAM ELEMENT NO. 61102F	PROJECT NO. 2303
		TASK NO. B2	WORK UNIT ACCESSION NO.
11. TITLE (Include Security Classification)			
A NEW APPROACH TO HIGHLY FLUORINATED LUBRICANTS Final Report			
12. PERSONAL AUTHOR(S)			
R.D. Chambers, P.T. Telford & M.W.H. West, Final Report			
13a. TYPE OF REPORT		13b. TIME COVERED	
Final		FROM 1.9.82 TO 31.8.87	
14. DATE OF REPORT (Year, Month, Day)		15. PAGE COUNT	
1987, October, 30		30	
16. SUPPLEMENTARY NOTATION			
17. COSATI CODES			
FIELD	GROUP	SUB-GROUP	
18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)			
Fluorinated Polyethers, direct fluorination, polymer modification, cobalt trifluoride, GREAT BRITAIN			
19. ABSTRACT (Continue on reverse if necessary and identify by block number)			
1. Various model ethers were modified by free-radical additions of F-alkenes. e.g. $[\text{CH}_3\text{CH}_2\text{OCH}_2]_2 + \text{CF}_2=\text{CFCH}_3 \longrightarrow (\text{CH}_3\text{CHR}_f\text{OCHR}_f\text{CH}_2\text{OCHR}_f\text{CH}_3)$ (where $R_f = \text{CF}_2\text{CFHCF}_3$ )			
2. These adducts were then fluorinated by cobalt trifluoride to give corresponding perfluoro-ethers. e.g. $\text{CH}_3\text{CHR}_f\text{OCHR}_f\text{CH}_2\text{OCHR}_f\text{CH}_3 \xrightarrow{i} \text{CF}_3\text{CFR}_f\text{OCFR}_f\text{CF}_2\text{OCFR}_f\text{CF}_3$ i, $\text{CoF}_3$ where $R'_f = \text{CF}_2\text{CF}_2\text{CF}_3$			
(Continued)			
20. DISTRIBUTION/AVAILABILITY OF ABSTRACT		21. ABSTRACT SECURITY CLASSIFICATION	
<input checked="" type="checkbox"/> UNCLASSIFIED/UNLIMITED <input type="checkbox"/> SAME AS RPT <input type="checkbox"/> DTIC USERS		Unclassified	
22a. NAME OF RESPONSIBLE INDIVIDUAL		22b. TELEPHONE (Include Area Code)	22c. OFFICE SYMBOL
Dr Anthony J. Matuszko		(202) 767-4963	NC

DD FORM 1473, 84 MAR

83 APR edition may be used until exhausted.  
All other editions are obsolete.


SECURITY CLASSIFICATION OF THIS PAGE

Unclassified



87 12 29 301

## 19. ABSTRACT (Continued)

3. Factors affecting the additions of F-alkenes to ethers have been explored as models for corresponding reactions with polyethers.
4. Techniques for direct fluorination of adducts of model ethers have been developed



5. Modification of polyethers extensively with F-alkenes has been developed successfully to give a range of new materials that will be useful to industry.



6. Poly-adducts of various poly-ethers have been successfully fluorinated by elemental fluorine, to give perfluorinated oils.

Accession For	
NTIS CRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	
Distribution/	
Availability Codes	
Date	Indexing/
A-1	



### Completed Project Summary

Title: A New Approach to Highly Fluorinated Lubricants

Principal Investigator: Professor Richard D. Chambers,  
Department of Chemistry,  
University of Durham,  
South Road,  
DURHAM, DH1 3LE,  
U.K.

Inclusive Dates: 1st September 1982-31st August 1987

Contract/Grant Number: AFOSR 82-0084

Costs and Fy source: \$19,556, FY82; \$19,769, FY83; \$20,568, FY84;  
\$19,988, FY85; \$21,341, FY86.

Senior Research Personnel: Professor Richard D. Chambers

Junior Research Personnel: Dr. Peter T. Telford  
Mr. Michael W.H. West

Technical Assistance: Mr. T.F. Holmes  
Mr. D. Hunter  
Mr. C.D. Hewitt

#### Publications:

"Polyether Compounds and their Preparation", R.D. Chambers, U.K. Patent Application No. 86.12983 (1986).


"Model Compounds in the Preparation of Fluorinated Ethers", R.D. Chambers, P.T. Telford, and M.W.H. West, manuscript in preparation for the Journal of Fluorine Chemistry.

"Modification of Polyethers, using Fluorinated Alkenes", R.D. Chambers, P.T. Telford, and M.W.H. West, manuscript in preparation for J.C.S. Perkin Trans. 1.


"New Routes to Highly Fluorinated Ethers", Ph.D. thesis, University of Durham, 1986 (Restricted access for six years).

#### Abstract of Objectives and Accomplishments:

1. Various model ethers were modified by free-radical additions of F-alkenes.




2. These adducts were then fluorinated by cobalt trifluoride to give corresponding perfluoro-ethers.





3. Factors affecting the additions of F-alkenes to ethers have been explored as models for corresponding reactions with polyethers.

4. Techniques for direct fluorination of adducts of model ethers have been developed



5. Modification of polyethers extensively with F-alkenes has been developed successfully to give a range of new materials that will be useful to industry.



6. Poly-adducts of various poly-ethers have been successfully fluorinated by elemental fluorine, to give perfluorinated oils.

Grant Number AFOSR 82-0084

A NEW APPROACH TO HIGHLY FLUORINATED LUBRICANTS

Richard D. CHAMBERS, Peter T. Telford & Michael W.H. West

Department of Chemistry,  
University of Durham,  
Science Laboratories,  
South Road,  
Durham, DH1 3LE, U.K.

30th October, 1987.

Final Report, 1st September 1982 - 31st August 1987.

Approved for public release;  
distribution unlimited.

Prepared for AFDW/AFMCSC  
Bolling AFB DC 20332-5260

and European Office of Aerospace Research & Development,  
223/231 Marylebone Rd.,  
London, England.

distribution unlimited






## Introduction


Perfluorinated polyethers constitute an important class of materials that demonstrate exceptional chemical and thermal stability,<sup>1</sup> amongst organic liquids, and some of these materials show good lubricant properties.<sup>2</sup> Consequently, such materials are of especial interest to the U.S.A.F. as lubricants in aggressive environments and, particularly, as potential liquid lubricants for high-temperature/high-efficiency aero-engines.

The aim of this project is to explore new approaches to the synthesis of perfluorinated ethers because the main problem that limits the wider application of industrially available materials is their high cost, which is an inevitable consequence of the limited methodology available. These approaches are essentially:

1. Polymerisation of Perfluoro-epoxides<sup>3</sup> ('Krytox' fluids, Du-Pont Co.)

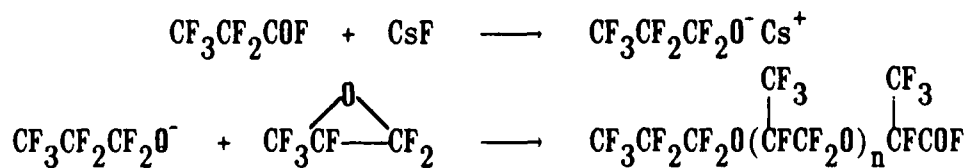


2. Photochemical Oxidation/Polymerisation of F-Alkenes<sup>4</sup> ('Fomblin' fluids, Montefluos Co.)




(Each of the above approaches are followed by end-group stabilisation.)

3. Polymerisation of a Fluorinated Oxetane, followed by Direct Fluorination<sup>5</sup>  
('Demnum' fluids, Daikin Co.)

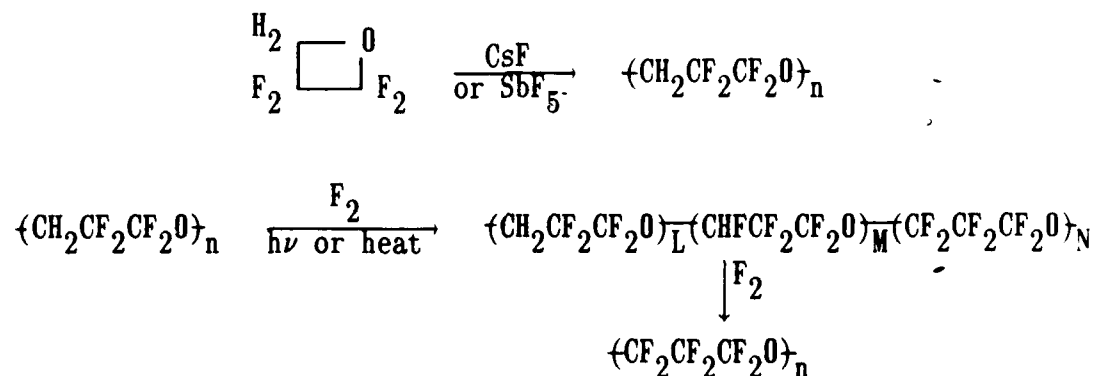


The present project involves the development of a two-stage approach to perfluoropolyethers based on modification of polyethers of known molecular-weight range. A severe disadvantage of existing methodology, outlined above, is that each approach involves a polymerisation stage with a consequent range of molecular-weight in the product. If this could be avoided, as in the present approach, then it would have very considerable advantage. Two stages are involved in the present approach: (A) involving addition of a perfluoroalkene to a polyether and (B) development of fluorination techniques for fluorination of the product polyadducts (1) from (A).

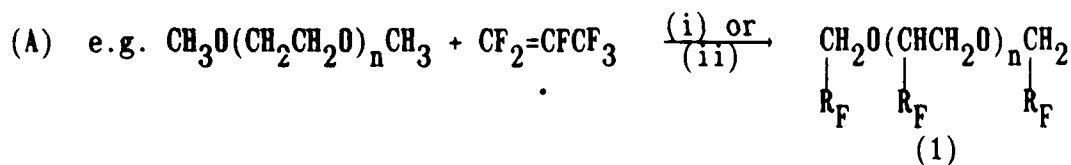

(where  $\text{R}_F = \text{CF}_2\text{CFHCF}_3$ )

(i) = Peroxide, heat    (ii) =  $\gamma$  ray initiation

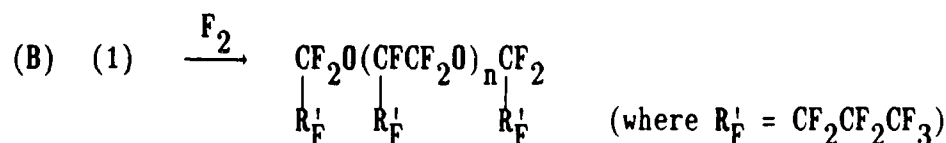


### Model Compound Studies

The first phase of the work was to explore the use of model compounds, in order to develop technique. This is more effective than working directly on high molecular-weight material because of the obviously easier identification procedures involved.

### Free-Radical Additions of F-Propene to Ethers


The normal radical-chain process is involved in addition of ethers to e.g. F-propene but there are two features to stress.<sup>6</sup> First, a radical derived from an ether is stabilised by interaction with the non-bonding electron-pair on oxygen.

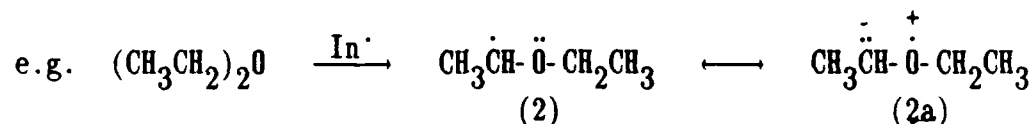


(where  $In\cdot$  = initiating radical.)

As a consequence of this interaction these radicals are quite nucleophilic in character and, consequently, are extremely reactive towards F-alkenes which are, of course, electrophilic in character.

The second feature to stress is the fact that, after addition to the fluorinated alkene, the intermediate radical (3) is ideally orientated for a 1-5 transfer of a hydrogen atom. Therefore, the di-adduct (5) is produced in competition with the mono-adduct (4). The fact that this intramolecular process occurs follows from the fact that the mono-adduct (4) is not easily converted to (5) under conditions where (5) may be obtained in good yield when starting from the diethylether.

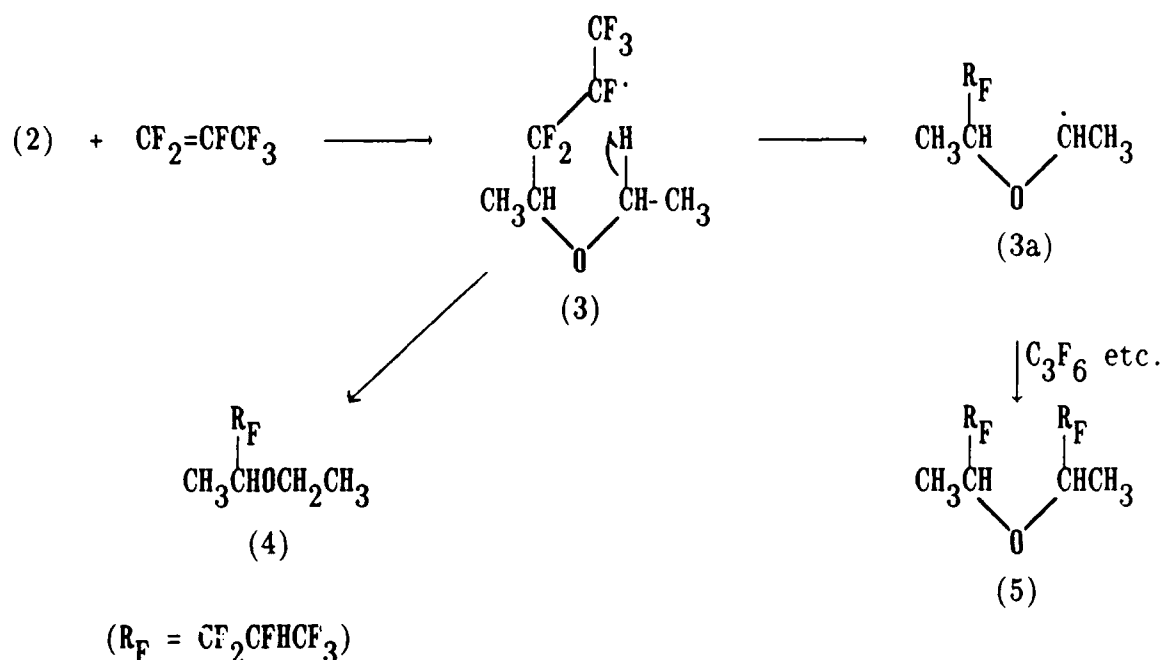


This latter observation highlights a third factor which affects additions of ethers to F-alkenes i.e. the influence of electron-withdrawing substituents. We have already drawn attention to the fact that (2) is especially reactive because the radical is nucleophilic. However, the converse effect applies on the reactivity of the chain-propagating radical (7) with an ether that is partly fluorinated. The propagating radical (7) is

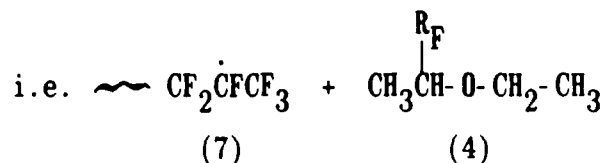






electrophilic in character and the ether adduct (4) is made more electrophilic by introduction of the polyfluoroalkyl group. Hence, this combination is less reactive than a system which involves diethylether itself. Entropy factors, of course, favour the intramolecular hydrogen transfer in (3).

The points outlined above are highly relevant to the additions that follow and additions of F-propene to a variety of model compounds are now described.

A comparison of terminal methoxy and ethoxy derivatives revealed a very clear difference in reactivity. The ethoxy derivatives showed a preference for attack at the ethoxy group and this usually led to a greater degree of addition of F-propene units than with methoxy compounds. This undoubtedly stems from the easier hydrogen abstraction from secondary ethoxy sites, followed then by the intramolecular hydrogen transfer processes like that illustrated in (3).



$\text{R}_\text{F} = \text{CF}_2\text{CFHCF}_3$ ; (i),  $\gamma$ -ray initiator,  $20^\circ\text{C}$




Ether:  $\text{C}_3\text{F}_6$  3:1 (% yields), 1:2 [% yields]

We were able to conclude from these experiments that the order of reactivity of various sites is:




Consequently, we concluded that the use of ethoxy end-groups would be particularly useful in higher molecular-weight ethers, both to make certain that end group are reactive and that the maximum number of additions to F-propene takes place.

It is important to stress that in no case have we observed the addition of two F-propene units to the same carbon site.



The fact that compound (11) is a major product derived from (8) follows from the intramolecular transfer mechanism.

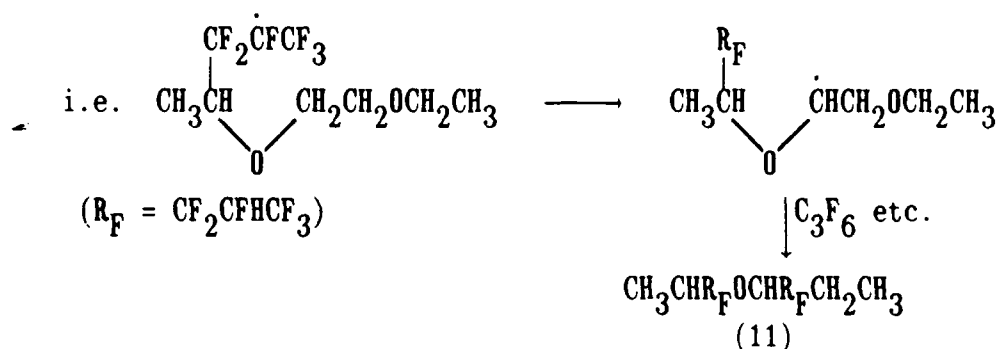


Similarly, the formation of isomer (11) in considerable preference to (12), may be explained on the same basis. As we increase the ratio of F-propene, then the extent of addition increases and the tri-adduct (14) is formed with excess alkene. It may be obtained as the major product if a



TABLE 1. Acetone:Butanol ratios (140°C)

<u>Substrate</u> <sup>†</sup>	<u>Ratio</u>
$[\text{CH}_3\text{CH}_2\text{OCH}_2]_2$ (8)	0.1
$\text{CH}_3\text{CH}_2\text{OCH}_2\text{CH}_2\text{OCHR}_\text{F}\text{CH}_3$ (10)	0.9
$\text{CH}_3\text{CH}_2\text{OCH}_2\text{CHR}_\text{F}\text{OCH}_2\text{CH}_3$ (9)	1.9
$\text{CH}_3\text{CH}_2\text{OCH}_2\text{CHR}_\text{F}\text{OCHR}_\text{F}\text{CH}_3$ (11)	2.5
$[\text{CH}_3\text{CHR}_\text{F}\text{OCH}_2]_2$ (13)	75
$\text{CH}_3\text{CHR}_\text{F}\text{OCH}_2\text{CHR}_\text{F}\text{OCHR}_\text{F}\text{CH}_3$	No BuOH detected



Additions of diethylether and other ethers to a variety of F-alkenes and -cycloalkenes are summarised in TABLE 2. Additions to diethylether reveal that fluoro-ethenes prefer to participate in telomerisation reactions, rather than intramolecular hydrogen transfer, which would have given di-adducts i.e.  $(\text{CH}_3\text{CHR}_\text{F})_2\text{O}$ . Perfluorocyclopentane and -cyclohexane give substantial amounts of the di-adducts whereas only a low yield of di-adduct is obtained with perfluorocyclobutene, indicating that ring size of the cyclic F-alkene has a significant effect on hydrogen-transfer.

#### Effect of Temperature




Additions of F-propene to  $(\text{EtOCH}_2)_2$  were investigated with gamma-rays at 20°C and with  $(\text{tBuO})_2$  at 140°C and the following conclusions were drawn from the results: (a) initial radical attack on the ether is less selective at the higher temperature but still favours the ethyl end-groups and (b) the



TABLE 2. Free-Radical Additions of F-Alkenes and -Cycloalkenes to Ethers  
( $\gamma$ -ray Initiation, 20°C)

Reactants	Products (Yield)
$\text{Et}_2\text{O} + \text{CF}_2=\text{CFCF}_3$	$\text{CH}_3\text{CHR}_\text{F}\text{OCH}_2\text{CH}_3 + (\text{CH}_3\text{CHR}_\text{F})_2\text{O}$ (57%) (43%) $(\text{R}_\text{F} = \text{CF}_2\text{CFHCF}_3)$
$\text{Et}_2\text{O} + \text{CF}_2=\text{CFCl}$	$\text{CH}_3\overset{\text{CF}_2\text{CFC1H}}{\underset{ }{\text{CHOCH}_2\text{CH}_3}} + \text{CH}_3\overset{(\text{CF}_2\text{CFC1})_n\text{H}}{\underset{ }{\text{CHOCH}_2\text{CH}_3}}$ (90%) (10%) $n = 2, 3$
$\text{Et}_2\text{O} + \text{CF}_2=\text{CFH}$	$\text{CH}_3\overset{\text{CF}_2\text{CFH}_2}{\underset{ }{\text{CHOCH}_2\text{CH}_3}} + \text{CH}_3\overset{(\text{CF}_2\text{CFH})_n\text{H}}{\underset{ }{\text{CHOCH}_2\text{CH}_3}}$ (80%) (16%) $n = 2, 3$
$\text{Et}_2\text{O} + \boxed{\text{F}} \parallel$	$\text{CH}_3\text{CHR}_\text{F}\text{OCH}_2\text{CH}_3 + (\text{CH}_3\text{CHR}_\text{F})_2\text{O}$ $\text{R}_\text{F} = \boxed{\text{F}} \overset{\text{H}}{\diagup}$ (90%) (5%)
$\text{Et}_2\text{O} + \begin{array}{c} \diagup \\   \text{F} \\ \diagdown \end{array}$	$\text{R}_\text{F} = \begin{array}{c} \diagup \\   \text{F} \\ \diagdown \end{array} \text{H} \quad (60\%) \quad (27\%)$
$\text{Et}_2\text{O} + \begin{array}{c} \diagup \\   \text{F} \\ \diagdown \end{array}$	$\text{R}_\text{F} = \begin{array}{c} \diagup \\   \text{F} \\ \diagdown \end{array} \text{H} \quad (40\%) \quad (40\%)$
$(\text{EtOCH}_2)_2 + \boxed{\text{F}} \parallel$	$\left. \begin{array}{l} \text{EtOCH}_2\text{CH}_2\text{OCHR}_\text{F}\text{CH}_3 \\ + \text{EtOCH}_2\text{CHR}_\text{F}\text{OEt} \end{array} \right\} (50\%)$ + Di-adducts (16%)

TABLE 2 continued

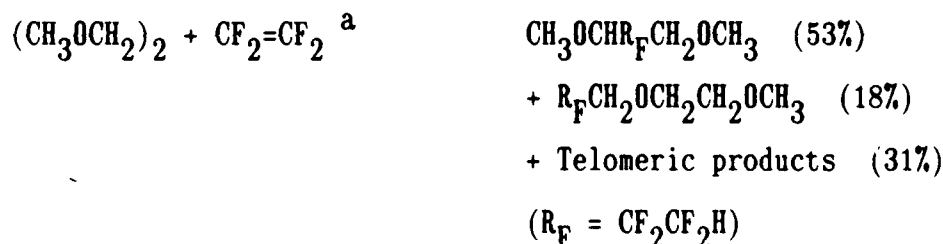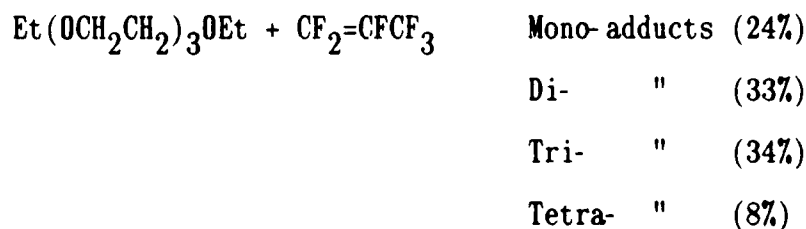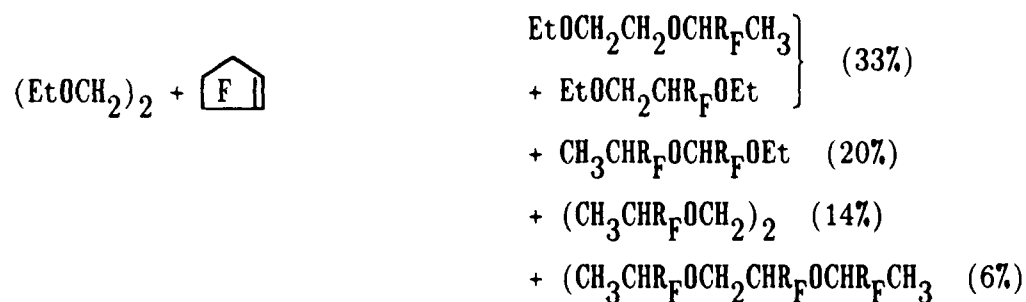

<sup>a</sup> Initiated by (tBuO)<sub>2</sub>, 140°C.

1,5-hydrogen transfer process, although still significant, is no in competition with a step-wise process that can occur at higher temperatures.

### General Conclusions

These model compound studies provide a sound basis of understanding for corresponding polyether modification, which is described in the next section.

### Adducts to Polyethers

Remarkably, modification of polyethers by free-radical additions of fluorinated alkenes have not been reported. To maximise reactivity, we prepared di-ethyl derivatives using a range of commercially available polyethyleneglycols.

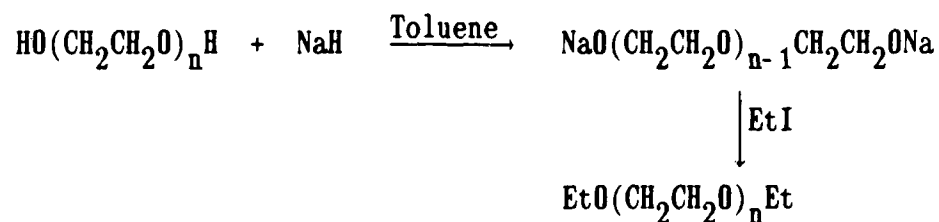



TABLE 3

<u>Glycol</u>	<u>Glyme</u>	<u>M.Wt. of Glyme</u>	<u>Yield (%)</u>
[Abbreviation]	[Abbreviation]		
$\text{HO}(\text{CH}_2\text{CH}_2\text{O})_{8-9}\text{H}$ [PEG 400]	$\text{EtO}(\text{CH}_2\text{CH}_2\text{O})_{8-9}\text{Et}$ [DEPEG 400]	~456	74
$\text{HO}(\text{CH}_2\text{CH}_2\text{O})_{13}\text{H}$ [PEG 600]	$\text{EtO}(\text{CH}_2\text{CH}_2\text{O})_{13}\text{Et}$ [DEPEG 600]	~656	69
$\text{HO}(\text{CH}_2\text{CH}_2\text{O})_{45}\text{H}$ [PEG 2000]	$\text{EtO}(\text{CH}_2\text{CH}_2\text{O})_{45}\text{Et}$ [DEPEG 2000]	~2056	66

Free-radical additions of F-propene to the glymes was carried out using ditertiarybutylperoxide or gamma-rays as initiator and the products showed

considerable incorporation of F-propene into the polyether backbone (see Table 4). The degree of incorporation was determined by adding a known weight reference compound (trifluoromethylbenzene) to a sample of the adduct and then comparing H-1 and F-19 n.m.r. spectra.

The ethyl end-groups are substituted, as anticipated, and then incorporation into the backbone occurs. These poly-adducts are discussed in

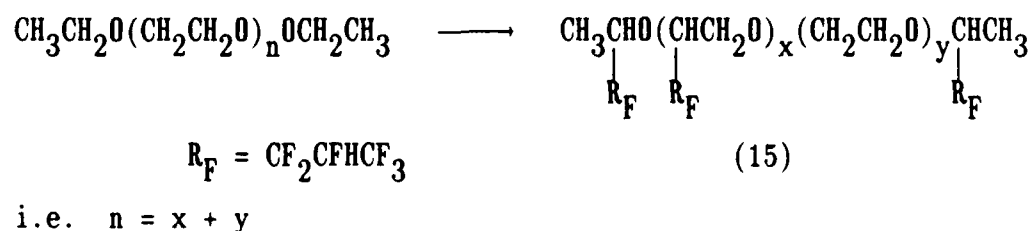

terms of a general structure (15) but, beyond establishing from n.m.r. data, that the end-groups are substituted, we have no way at this stage of determining the distribution of the fluorinated groups along the backbone.


However, from our model-compound studies described earlier, we may assume that not more than one addition takes place per  $\text{CH}_2\text{CH}_2\text{O}$  group. Scale-up of these reactions has also been successfully achieved.

TABLE 4. Adducts from Glymes and F-Propene [see structure (15)]

<u>Glyme</u>	<u>X</u>	<u>Y</u>	<u>Yield (%)</u>	<u>M.Wt. (Calc.)</u>
DEPEG 400	4-5	4.5-3.5	86	~1431
DEPEG 600	9-10	4-3	84	~2306
DEPEG 2000	18	27	80	~5056

We have reacted the initial product from DEPEG 600 with more F-propene in considerable excess and obtained the product where  $x = 13$  and we have also demonstrated that products from DEPEG 2000 can also be reacted further.

Diethyl derivatives of polytetrahydrofuran were reacted with F-propene in a similar way and it is very noticeable that this system leads to considerably increased incorporation of hexafluoropropene. This undoubtedly arises because the  $\text{OCH}_2$  units are separated by a larger number of units so that, on introduction of a polyfluoroalkyl group, the deactivating influence  $-\text{OCHR}_\text{F}\text{CH}_2\text{CH}_2\text{CH}_2-\text{O}-$  is much attenuated in comparison with glycol units i.e.  $-\text{OCHR}_\text{F}\text{CH}_2\text{O}-$  which, as we have seen, are considerably deactivated towards further attack.

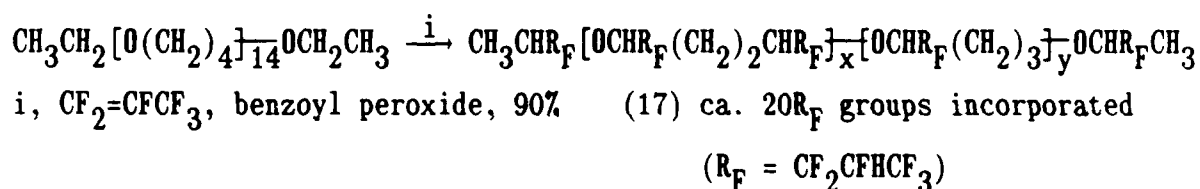

Structure (17) is also an average formula because we have little information on the distribution of  $\text{R}_\text{F}$  groups along the chain except to know that the end-groups are substituted. However, by adding further F-propene to the product it is possible to obtain a product where virtually each site adjacent to oxygen has been modified to an  $\text{OCHR}_\text{F}$  unit.





This process is quite remarkable because we are using the polyether backbone to introduce quite dramatically large quantities of F-alkene and it is certain that these products will become industrially significant in their own right.


## Fluorination of Adducts

### (a) Cobalt Trifluoride

Although mass-spectrometry and n.m.r. were very useful, an additional and helpful tool of characterisation of the model compounds was conversion to the corresponding perfluorinated ether, by passing over cobalt trifluoride. Note that, in the absence of perfluoroalkyl groups in the system to be fluorinated, extensive fragmentation occurs. In earlier work from this laboratory, we have demonstrated the value of perfluoroalkyl groups being present.<sup>7</sup>

In this way, various perfluoroethers were characterised, thus demonstrating the structures of the corresponding precursor adducts. This is made possible because of the easier interpretation of F-19 n.m.r. spectra than corresponding H-1 spectra of the precursor adducts.

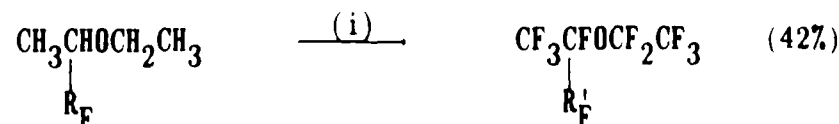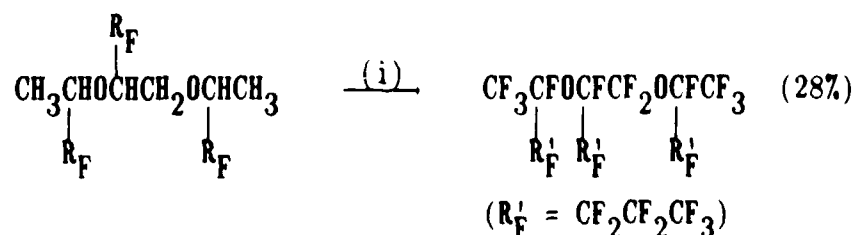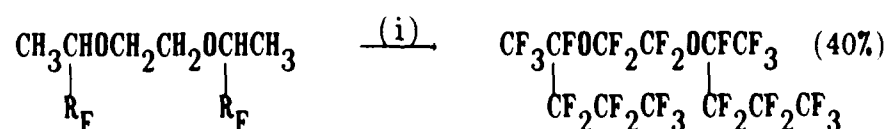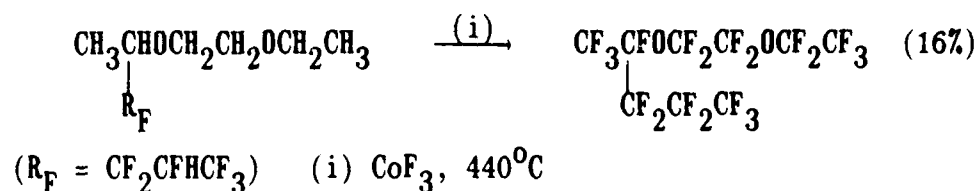

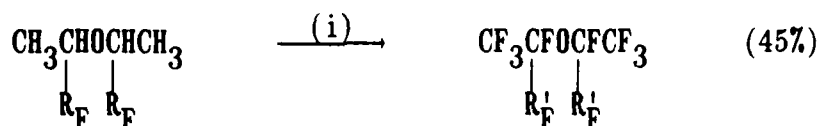


(b) Direct Fluorinations


Clearly, cobalt trifluoride cannot be used to fluorinate high molecular-weight material using conventional technology. Therefore, we have developed direct fluorination for this purpose. A 10 amp fluorine generator was built, to provide 100%  $\text{F}_2$  and concentrations in nitrogen above 50%. We have also employed 50%  $\text{F}_2$  in  $\text{N}_2$ , that is commercially available in cylinders. For safety reasons we have avoided 100%  $\text{F}_2$  in large-scale cylinders.

Reactivity of Simple Adducts towards Fluorine

We here used some simple 1:1 adducts (8)-(10) and treated these with fluorine, diluted with nitrogen, and cooled to  $-80^\circ\text{C}$ . However, we found it difficult to control the fluorination of these materials without ignition, especially if these materials were present in the vapour phase.

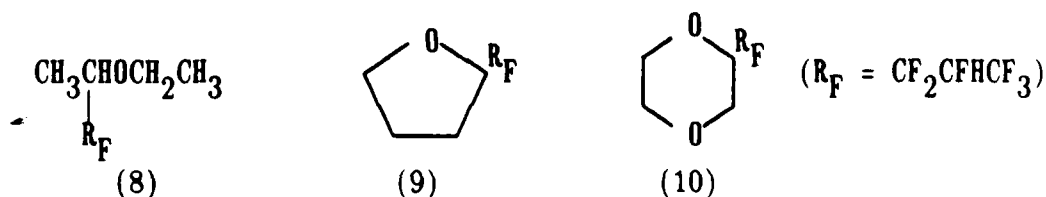



In contrast, however, di-adducts showed remarkable stability to fluorine. For example, we have now found that the di-adduct (11) will react smoothly with fluorine at  $20^\circ\text{C}$ . Therefore, using a very simple procedure, of passing fluorine/nitrogen into a column of the liquid then extensive fluorination may be obtained, as indicated.

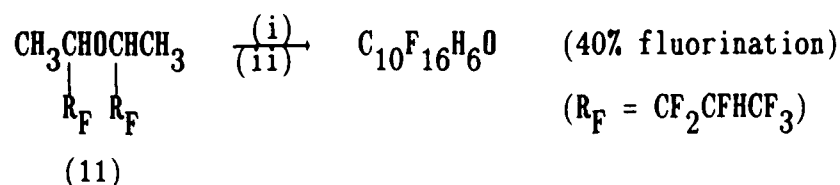

(i), 25%  $\text{F}_2/\text{N}_2$  20°C-60°C (5 h) (ii), 50%  $\text{F}_2/\text{N}_2$  20°C-60°C (5 h)


These are not optimised conditions and it now seems clear that the process may be completed quickly at the higher temperature. The only losses are not due to fragmentation but to the volatility of the starting material and products.

Further treatment of the mixture  $\text{C}_{10}\text{F}_{16}\text{H}_6\text{O}$ , with 100% fluorine, gave further fluorination but, remarkably, only 75% fluorination could be achieved at temperatures up to 100°C. The chemical resistance of even these partly fluorinated compounds is, therefore, quite outstanding.

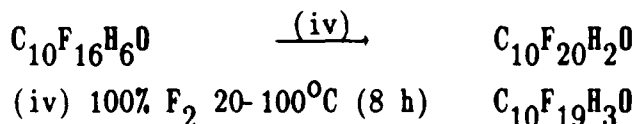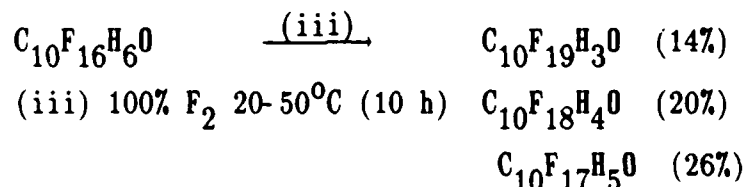

#### Sealed-Tube Fluorination


At these higher temperatures, loss by evaporation is considerable (this is not, of course, a problem with the high molecular-weight materials) and we therefore condensed fluorine into a steel tube containing the  $\text{C}_{10}\text{F}_{16}\text{H}_6\text{O}$  mixture.

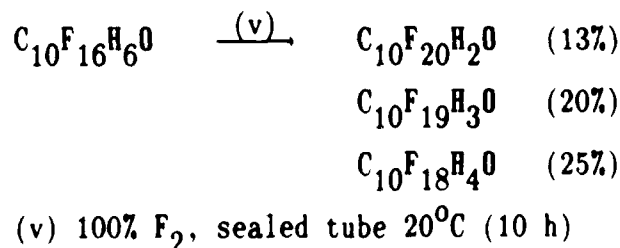



Remarkably, the system not only survived this treatment but, also, fluorination was still not complete. This was, however, completed by using the same sealed tube procedure, and a temperature of 40°C.

It is a clear illustration of the stability of these compounds, that such simple and drastic procedures may be applied to such effect. The recorded yields are not optimised at all and, no doubt, much higher yields may be obtained with more development. However, the virtue of this approach, of

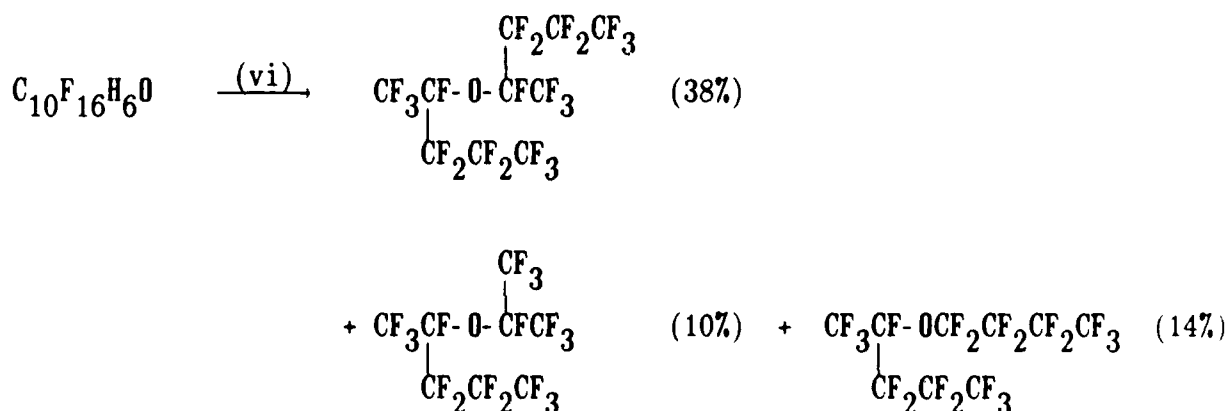


(vi) 100% F<sub>2</sub>, sealed tube 40°C (24 h).

introducing polyfluoroalkyl groups through fluorinated alkenes prior to fluorination lies in the simplicity of the conditions required for the subsequent stages of fluorination.

#### Viscosity of Intermediate Stages

In the course of these fluorinations of adducts, we have observed that a stage is often reached where the medium becomes exceedingly viscous. At first, we deduced that fluorine-induced coupling of ethers was occurring (this would have been an interesting phenomena). However, we took these partly fluorinated, viscous materials, in some cases and subjected them to fluorination over cobalt trifluoride. In each case, the perfluoroether which

corresponds to the original adduct was obtained, demonstrating that no coupling or change in the carbon-oxygen skeleton had occurred.

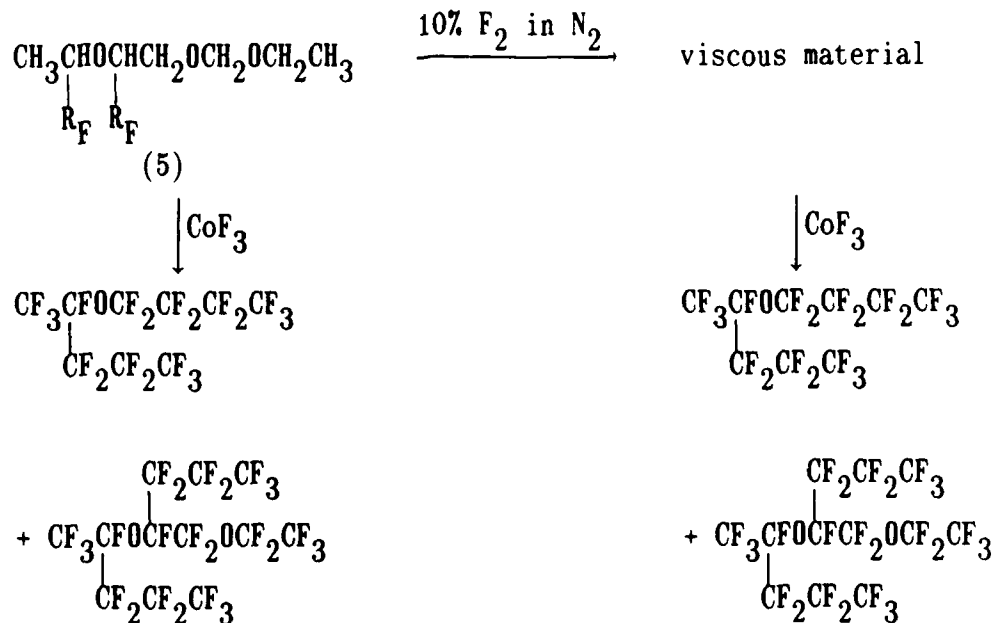

We may assume, therefore, that this dramatic change in viscosity, on partial fluorination, is a consequence of increased intermolecular hydrogen-bonding. Needless to say, the corresponding perfluoroethers are mobile ligands.

#### Fluorination of Higher Molecular-Weight Materials

These studies have been carried out in two stages:


- (i) Bubbling  $\text{F}_2/\text{N}_2$  mixtures through the adducts, without any elaborate procedures. It is a remarkable feature of these systems that this direct fluorination can be carried out in quite simple apparatus, that can therefore be scaled up. Generally, the concentration of fluorine is increased in the following sequence

25% F<sub>2</sub>/N<sub>2</sub> at 20°C

25% F<sub>2</sub>/N<sub>2</sub> at 50°C

50% F<sub>2</sub>/N<sub>2</sub> at 50°C

- (ii) Final removal of remaining hydrogen was completed by exposing to 100% F<sub>2</sub> in a sealed system. Significant effort is being expended to understand the factors affecting the outcome of this stage, including the effect of pressure.

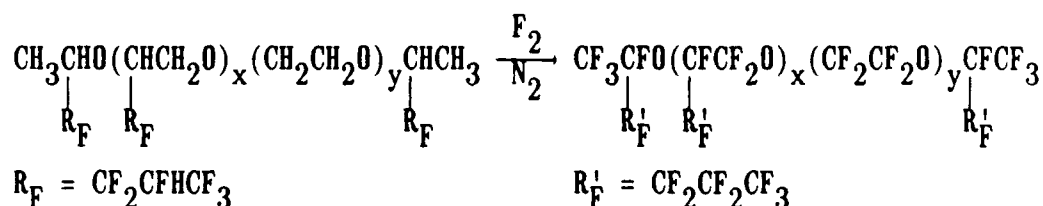

<u>Adduct</u>	<u>x</u>	<u>y</u>	<u>Yield of<sup>b</sup></u>	<u>Anticipated</u>
			<u>Perfluoroether (%)</u>	<u>Average M.Wt.</u>
DEPEG 400	4/5	4-5/3-4	31	2230
DEP 600	9/10	4/3	27	3410
DEP 2000	18	27	34	~8500

<sup>b</sup>-This stage has not been carried out on a large scale and handling losses are therefore exaggerated.

In each case, the final product was examined carefully by F.T. <sup>1</sup>H-n.m.r. and no significant amount of H could be detected, confirming that a perfluoropolyether had been obtained. Thus, we have now demonstrated that the technique can be applied equally to materials of a wide range of molecular-weight but the virtue, is the fact that products of high molecular-weight may be obtained, if the appropriate starting material is used. (We have yet to measure molecular weights of the final products.)

We have been exploring more recently, larger-scale reactions in which the materials are fluorinated at atmospheric pressure, and at significantly higher temperatures. Fully fluorinated fluids are obtained and, at this stage, structural elucidation is still under way.

### Conclusions

1. Modification of polyethers by simple free-radical reactions with fluorinated alkenes occurs extensively and a range of opportunities for industry is opened by these new materials.
2. Preliminary work on direct fluorination of model adducts and subsequently, adducts of polyethers demonstrate that perfluorinated fluids may be obtained this way.
3. These studies are opening an alternative approach to some new perfluorinated polyether which could provide valuable materials to complement existing high-performance oils.

### Experimental

The following are examples which illustrate the general procedures used in the addition, oxidative fluorination and direct fluorination reactions.


All yields are based on g.l.c. analysis using a gas density balance detector. Column packings for this instrument are as follows: K = 20% Krytox (a commercial perfluoropolyether mixture; A = di-isodecylphthalate 30%; DNP = 10% di-nonylphthalate; 5% SE30 = 5% silicone elastomer.

NMR data: all shifts quoted are;  $^{19}\text{F}$  upfield from  $\text{CFCl}_3$ ;  $^1\text{H}$  downfield from TMS. For multiplicity of NMR: S = singlet, D = doublet, T = triplet, M = multiplet.

# Free-Radical Addition of Ethyl Glyme to Hexafluoropropene

## Technique

Ethyl glyme (5.9 g, 0.05 mol) and hexafluoropropene (17.1 g, 0.114 mol) were irradiated on a  $\text{Co}^{60}$  source (60 hrs, 200 Krads  $\text{hr}^{-1}$ ). The liquid products (16.5 g) were distilled using conventional apparatus to yield the adducts 4a (5%) b.p.<sub>40</sub> 79°C; 4b (16%) b.p.<sub>40</sub> 90°C; 5a,5b (22%) b.p.<sub>10</sub> 94°C; 5c (16%) b.p.<sub>6</sub> 106°C; all previously characterised<sup>8</sup> and in addition the tri-adducts, 6, (13%).

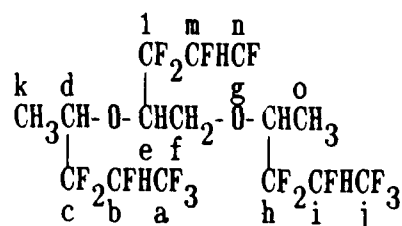

1,1,1,2,3,3,10,10,11,12,12,12-dodecafluoro-4,9-dimethyl-6-[1,1,2,3,3,3,hexafluoro-propyl]-5,8-dioxadodecane (Found C, 31.7; H, 2.46; F, 60.6%;  $\text{C}_{15}\text{F}_{18}\text{H}_{14}\text{O}_2$  requires C, 31.96; H, 2.45; F, 60.2%).

## $^{19}\text{F}$ NMR

	<u>Multiplicity</u>	<u>Shift</u>	<u>JHz</u>	<u>Rel. Intensity</u>	<u>Assignment</u>
	M	73.1		3	a,j,n
	M	121.7		2	c,h,l
	M	214.3		1	b,i,m

## $^1\text{H}$ NMR

	M	1.55		6	o,k
	M	4.07		5	e,f,d,g
	D of M	5.29	35	3	b,i,

m/z (chemical ionisation, isobutane +ve) 569 ( $\text{M}^+$ , 2.2%), 373 (2.0), 223 (1.5), 97 (1.5), 85 (4.8), 81 (3.8), 79 (2.9), 69 (9.6).

### Addition of Diethyl Diglyme to Hexafluoropropene

#### Technique


Diethyl diglyme (4.05 g, 0.025 mol) was placed in a nickel tube fitted with a valve and degassed using freeze thaw cycles under vacuum. Hexafluoropropene (14.66 g, 0.098 mol) was transferred, under vacuum, into the tube and the valve closed. The tube was then irradiated on the  $\text{Co}^{60}$  source for 72 hrs. ( $200 \text{ Krads hr}^{-1}$ ). The tube was cooled (liquid air) opened to a vacuum and hexafluoropropene (4.48 g, 0.029 mol) recovered by allowing the tube to warm. The liquid products (12.9 g) containing eleven components (g.l.c. col. K  $180^\circ\text{C}$ ) were distilled using conventional apparatus to give isomer mixtures, determined by chemical ionisation mass spectrometry/capillary g.l.c. techniques and consistent NMR data, mono-adducts,  $\text{C}_{11}\text{H}_{18}\text{F}_6\text{O}_3$  (24%) b.p.  $5$   $80-90^\circ\text{C}$ ; di-adducts,  $\text{C}_{14}\text{H}_{18}\text{F}_{12}\text{O}_3$  (33%) b.p.  $5$   $100-110^\circ\text{C}$ ; tri-adducts,  $\text{C}_{17}\text{H}_{18}\text{F}_{18}\text{O}_3$  (34%) b.p.  $0.01$   $68^\circ\text{C}$ ; tetra-adducts,  $\text{C}_{20}\text{F}_{24}\text{H}_{18}\text{O}_3$  (8%) b.p.  $0.01$   $> 100^\circ\text{C}$ .

### Oxidative Fluorinations Using $\text{CoF}_3$

Fluorination of (6)  $\text{CH}_3\text{CH}(\text{R}_\text{F})\text{OCH}(\text{R}_\text{F})\text{CH}_2\text{OCH}(\text{R}_\text{F})\text{CH}_3$  ( $\text{R}_\text{F} = \text{CF}_2\text{CFHCF}_3$ )

#### Technique

The adduct (6) (1.58 g, 2.78 mmol) was passed over a cobalt trifluoride bed at  $440^\circ\text{C}$  in the usual manner.<sup>9</sup> The product mixture (1.12 g), containing five volatile and one less volatile components (g.l.c., col. A, 72%) was separated using preparative scale g.l.c. The less volatile component was characterised as perfluoro-4,9-dimethyl-6-propyl-5,8-dioxadodecane (28%) b.p.  $198^\circ\text{C}$  (Found C, 21.7; F, 74.32%.  $\text{C}_{15}\text{F}_{32}\text{O}_2$  requires C, 21.9; F, 74.14%)

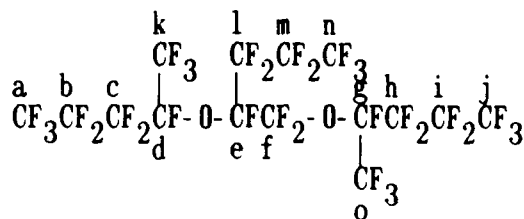

<u>Multiplicity</u>	<u>Shift</u>	<u>JHz</u>	<u>Rel. Intensity</u>	<u>Assignment</u>
M	79.6		2	f
M	79		3	k,o
M	81.3		3	
T of M	84	10.4	9	a,n,j
M	122		6	h,l,c
M	127.8		6	b,m,i
M	135.2		2	d,e
M	143.5		1	g

## Fluorinations Using Elemental Fluorine

### Direct fluorination of di-(1-methyl-2,2,3,4,4,4-hexafluorobutyl)ether


### Technique

Di-(1-methyl-2,2,3,4,4,4-hexafluorobutyl)ether (4.7 g, 12.6 mmol) was placed in the reactor vessel and the system flushed with nitrogen for 20 minutes. Nitrogen was shut off and a mixture of 25% fluorine in nitrogen was passed through the adduct at 20°C for two hours, then at 60°C for three hours. Further fluorination was then effected using a 50% mixture of fluorine in nitrogen; this was bubbled through the partially fluorinated mixture at 20°C for 2 hours then 60°C for three hours. The liquid products (4.25 g), containing 14 components (g.l.c. 5% SE30 102°C), were not separated due to the complexity of the mixture. Using g.l.c./mass spectrometry mass maxing

techniques it was possible to determine the molecular weights of the components:-  $C_{10}F_{15}H_7O$  (6%);  $C_{10}F_{16}H_6O$  (50%);  $C_{10}F_{17}H_5O$  (25%).


Direct Fluorination of the Mixture  $caC_{10}F_{16}H_6O$  Using a Sealed System Technique

The mixture (0.59 g, 1.32 mmol) was contained in a passified 70 ml nickel tube fitted with a monel valve and then degassed using freeze thaw cycles under vacuum. Fluorine (0.86 g, 22.7 mmol) was condensed into the tube by cooling in liquid nitrogen. The tube was allowed to warm to room temperature for eight hours before heating to  $40^{\circ}C$  for twenty-four hours. The system was then cooled to  $20^{\circ}C$ , vented and the liquid products (0.44 g) recovered. The product mixture, containing four components (g.l.c. col. A  $45^{\circ}C$ ), was separated using preparative scale g.l.c. techniques to give:- perfluoropentane (4%); perfluoro- [1-methyl-butyl]isopropyl ether (10.5%),

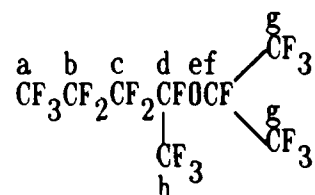


$^{19}F$ NMR	<u>Multiplicity</u>	<u>Shift</u>	<u>Rel. Intensity</u>	<u>Assignment</u>
	M	81.5	3	a
	M	83.5	3	h
	M	85	6	g
	M	124.6	2	c
	M	129	2	b
	M	137.5	1	d
	M	143.6	1	f



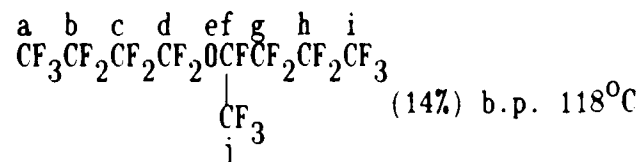

Perfluoro(1-methyl-butyl)butyl ether (Found C, 21.43; F, 74.8%.  $\text{C}_9\text{F}_{20}\text{O}$  requires C, 21.43; F, 75.39%).

$^{19}\text{F}$ NMR	Multiplicity	Shift	Rel. Intensity	Assignment
	M	81.6	3	j
	M	83.2	2	d
	M	84.2	6	a, i
	M	123.8	2	c
	M	128.3	6	b, g, h
		129		
	M	143	1	f

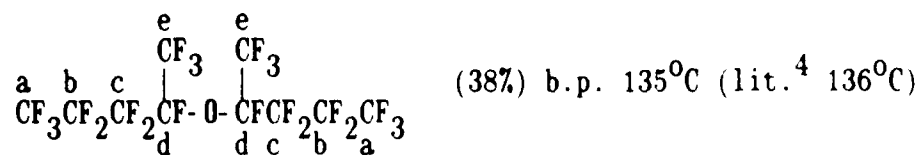

Perfluoro di-1-methyl-butyl ether (Found C, 21.4; F, 75.8% calculated for  $\text{C}_{10}\text{F}_{22}\text{O}$ ; C, 21.66; F, 75.45%).

<sup>19</sup> F NMR	<u>Multiplicity</u>	<u>Shift</u>	<u>JHz</u>	<u>Rel. Intensity</u>	<u>Assignment</u>
	M	80	}	6	e
	M	81.6			
	T of M	84.7		6	a
	M	118.6		4	c
	M	127.5			
	M	128.6		4	b
	M	137.6		2	d

### References

1. D. Sianesi, V. Zamboni, R. Fontanelli, and M. Binaghi, Wear, 1971, 18, 85.
2. C.E. Snyder, L.J. Gschwender, and W.B. Cambell, Lubr. Eng., 1982, 38, 41.
3. Technical Bulletin, 'Krytox Fluids', du Pont Co. U.S.A.; H. Millaner, W. Schwertfeger, and G. Siegemund, Angew. Chemie., Int. Edn., 1985, 24, p.165 and references contained.
4. Technical Bulletin, 'Fomblin Fluids', Montefluos Co.
5. Technical Bulletin, 'Demnum Fluids', Daikin Industries Ltd.
6. R.D. Chambers, B. Grievson, and N.M. Kelly, J.C.S. Perkin Trans. I, 1985, 2209.
7. R.D. Chambers, B. Grievson, F.G. Drakesmith, and R.L. Powell, J. Fluorine Chem., 1985, 29, 323.
8. Details published in progress reports.
9. A.K. Barbour, G.B. Barlow, and J.C. Tatlow, J. Appl. Chem., 1952, 2, 127.

END  
DATE  
FILMED

4- 88

DTIC